



Pony Testing International Group

报告编号(Report ID): W12313025221D~1

锂电池UN38.3测试报告

Lithium Battery UN38.3 Test Report

样品名称

(Samples)

Lithium-ion Battery APST 3S1P 18650

委托单位

(Client)

AccuPower Forschungs-, Entwicklungs- und

Vertriebsgesellschaft mbH

生产单位

(Manufacturer)

AccuPower Forschungs-, Entwicklungs- und

Vertriebsgesellschaft mbH

PONY 谱尼测试

Pony Testing International Group

www.ponytest.com

No.: W12313025221D

Code: czeemz



Pony Testing International Group

I、SAMPLE DESCRIPTION

Sample Name	Lithium-ion Battery		Battery Type	APST 3S1P 18650	
Client	AccuPower Forschungs-, Entwicklungs- und Vertriebsgesellschaft mbH				
Manufacturer	AccuPower Forschungs-, Entwicklungs- und Vertriebsgesellschaft mbH				
Nominal Voltage	11.1V	Rated Capacity	2600mAh	Limited Charge Voltage	12.6V
Charge Current	2000mA	Maximum Continuous Charge Current	2600mA	End Charge Current	100mA
Cut-off Voltage	7.5V	Maximum Discharge Current	3000mA	Use	Power Tool
Cells Number	3PCS	Cell Model	18650	Rated Capacity	2600mAh
Manufacturer of cell	SAMSUNG		Chemical component	Lithium-ion	
Client date	2012-12-17		Finished date	2013-01-06	

II、STANDARD

United Nations Recommendations On The Transport Of Dangerous Goods, Manual Of Tests And Criteria.

III、TEST ITEM

- | | |
|------------------------|---------------------------|
| 1. Altitude simulation | 5. External short circuit |
| 2. Thermal test | 6. Crush |
| 3. Vibration | 7. Overcharge |
| 4. Shock | 8. Forced discharge |

IV、CONCLUSION

ITEM	SAMPLE NUMBER	STANDARD	CONCLUSION
Altitude simulation	N1~N4 C1~C4	UN38.3	PASS
Thermal test			PASS
Vibration			PASS
Shock			PASS
External short circuit	N9~N13		PASS
Crush			PASS
Overcharge	N5~N8 C5~C8		PASS
Forced discharge	---		N/A (Not applicable)

The submitted battery and component cell were complied with the stated requirements of UN38.3.

Prepared by: *Zhengchun me*; Checked by: *sheng* Approved by: *P. Yao*

Approval Date: January 6, 2013

本检测单位保证检测的客观公正性，并对委托单位的商业秘密履行保密义务，委托单位对样品的代表性和资料的真实性负责，本检测单位仅对样品负责，委托单位对于检测结果的使用、使用所产生的直接或间接损失及一切法律后果，本检测单位不承担任何经济和法律责任；本《检测报告》如无PONY专用章和批准人签字或被复制，则无效；任何对本《检测报告》未经授权的部分或全部转载、篡改、伪造或复制行为都是违法的，将被追究民事、行政甚至刑事责任。

防伪说明：(1)《检测报告》的报告编号是唯一的，即每一个报告编号仅对应唯一的《检测报告》；
 (2)《检测报告》采用特制防伪纸张印制，纸张表面带有“PONY”防伪纹路，该防伪纹路不支持复印，即复制件不会带有“PONY”防伪纹路；
 (3)《检测报告》采用的防伪纸张内部亦加带有高科技“PONY”防伪水印，只有在验钞机等紫外线照射下方可见出无色荧光防伪字样；
 (4)《检测报告》所盖防伪骑缝章中的一部分加盖于本检测单位的留底报告上，《检测报告》与本检测单位留底报告的骑缝章应拼合完整无缺。

www.ponytest.com ☎Hotline 400-819-5688

Add: Yingzhi Building, No.49-3, Suzhou Road, Haidian District, Beijing	Building 35, No.680, Guiping Road, Xuhui District, Shanghai	Building 6 of Zhongxing Industry City, Chuangye Road, Nanshan District, Shenzhen	6th Floor, No.190, Zhuzhou Road, Laoshan District, Qingdao
Tel: (010)82618116	(021)64851999	(0755)26050909	(0532)88706866
Fax: (010)82619629	(021)64856403	(0755)26068336	(0532)88706877
E-mail: pony@ponytest.com	cs@ponytest.com	sz@ponytest.com	qd@ponytest.com

Pony Testing International Group



Pony Testing International Group

Notes:

N1~N8: Batteries at first cycle, in fully charged states;

N9~N13: Component cells of rechargeable batteries, at first cycle at 50% of the design rated capacity;

C1~C8: Batteries, after 50 cycles ending in fully charged states.

V. PHOTO OF THE SAMPLE



Authenticate the photo on original report only

本检测单位保证检测的客观公正性，并对委托单位的商业秘密履行保密义务；委托单位对样品的代表性和资料的真实性负责，本检测单位仅对样品负责，委托单位对于检测结果的使用、使用所产生的直接或间接损失及一切法律后果，本检测单位不承担任何经济和法律后果；本《检测报告》如无PONY专用章和批准人签字或被复制，则无效；任何对本《检测报告》未经授权的部分或全部转载、篡改、伪造或复制行为都是违法的，将被追究民事、行政甚至刑事责任。

防伪说明：(1)《检测报告》的报告编号是唯一的，即每一个报告编号仅对应唯一的《检测报告》；
 (2)《检测报告》采用特制防伪纸张印制，纸张表面带有“PONY”防伪纹路，该防伪纹路不支持复印，即复制件不会带有“PONY”防伪纹路；
 (3)《检测报告》采用的防伪纸张内部亦加带有高科技“PONY”防伪水印，只有在验钞机等紫外线照射下方可显出无色荧光防伪字样；
 (4)《检测报告》所盖防伪骑缝章中的一部分加盖于本检测单位的留底报告上，《检测报告》与本检测单位留底报告的骑缝章应拼合完整无缝。

www.ponytest.com ☎Hotline 400-819-5688

Add: Yingzhi Building, No. 49-3, Suzhou Road, Haidian District, Beijing	Building 35, No. 680, Guiping Road, Xuhui District, Shanghai	Building 607 Zhongxing Industry City, Chuangye Road, Nanshan District, Shenzhen	6th Floor, No. 190, Zhuzhou Road, Laoshan District, Qingdao
Tel: (010)82618116	(021)64851999	(0755)26050909	(0532)88706866
Fax: (010)82619629	(021)64856403	(0755)26068336	(0532)88706877
E-mail: pony@ponytest.com	cs@ponytest.com	sz@ponytest.com	qd@ponytest.com



Pony Testing International Group

VI、 TEST METHOD

Tests T.1 to T.5 shall be conducted in sequence on the same cell or battery. Tests T.6 and T.8 shall be conducted using not otherwise tested cells or batteries. Test T.7 may be conducted using undamaged batteries previously used in tests T.1 to T.5 for purposes of testing on cycled batteries.

In order to quantify the mass loss, the following procedure is provided:

$$\text{Mass loss(\%)} = (M_1 - M_2) / M_1 \times 100$$

Where M_1 is the mass before the test and M_2 is the mass after the test. When mass loss does not exceed the values in Table blow, it shall be considered as "no mass loss".

Mass M of cell or battery	Mass loss limit
$M < 1g$	0.5%
$1g \leq M \leq 75g$	0.2%
$M > 75g$	0.1%

T.1 Altitude simulation

Test cells and batteries shall be stored at a pressure of 11.6 kPa or less for at least six hours at ambient temperature ($20 \pm 5 \text{ }^\circ\text{C}$).

Cells and batteries meet this requirement if there is no leakage, no venting, no disassembly, no rupture and no fire and if the open circuit voltage of each test cell or battery after testing is not less than 90% of its voltage immediately prior to this procedure. The requirement relating to voltage is not applicable to test cells and batteries at fully discharged states.

T.2 Thermal test

Test cells and batteries are to be stored for at least six hours at a test temperature equal to $72 \pm 2 \text{ }^\circ\text{C}$, followed by storage for at least six hours at a test temperature equal to $-40 \pm 2 \text{ }^\circ\text{C}$. The maximum time interval between test temperature extremes is 30 minutes. This procedure is to be repeated until 10 total cycles are complete, after which all test cells and batteries are to be stored for 24 hours at ambient temperature ($20 \pm 5 \text{ }^\circ\text{C}$). For large cells and batteries the duration of exposure to the test temperature extremes should be at least 12 hours.

Cells and batteries meet this requirement if there is no leakage, no venting, no disassembly, no rupture and no fire and if the open circuit voltage of each test cell or battery after testing is not less than 90% of its voltage immediately prior to this procedure. The requirement relating to voltage is not applicable to test cells and batteries at fully discharged states.

本检测单位保证检测的客观公正性，并对委托单位的商业秘密履行保密义务；委托单位对样品的代表性和资料的真实性负责，本检测单位仅对样品负责，委托单位对于检测结果的使用、使用所产生的直接或间接损失及一切法律后果，本检测单位不承担任何经济和法律责任；本《检测报告》如无PONY专用章和批准人签字或被复制，则无效；任何对本《检测报告》未经授权的部分或全部转载、篡改、伪造或复制行为都是违法的，将被追究民事、行政甚至刑事责任。

防伪说明：(1)《检测报告》的报告编号是唯一的，即每一个报告编号仅对应唯一的《检测报告》；
(2)《检测报告》采用特制防伪纸张印制，纸张表面带有“PONY”防伪纹路，该防伪纹路不支持复印，即复制件不会带有“PONY”防伪纹路；
(3)《检测报告》采用的防伪纸张内部亦加带有高科技“PONY”防伪水印，只有在验钞机等紫外线照射下方可显出无色荧光防伪字样；
(4)《检测报告》所盖防伪骑缝章中的一部分加盖于本检测单位的留底报告上，《检测报告》与本检测单位留底报告的骑缝章应拼合完整无缺。



Pony Testing International Group

T.3 Vibration

Cells and batteries are firmly secured to the platform of the vibration machine without distorting the cells in such a manner as to faithfully transmit the vibration. The vibration shall be a sinusoidal waveform with a logarithmic sweep between 7 Hz and 200 Hz and back to 7 Hz traversed in 15 minutes. This cycle shall be repeated 12 times for a total of 3 hours for each of three mutually perpendicular mounting positions of the cell. One of the directions of vibration must be perpendicular to the terminal face.

The logarithmic frequency sweep shall differ for cells and batteries with a gross mass of not more than 12 kg (cells and small batteries), and for batteries with a gross mass of more than 12 kg (large batteries).

For cells and small batteries: from 7 Hz a peak acceleration of 1 g_n is maintained until 18 Hz is reached. The amplitude is then maintained at 0.8 mm (1.6 mm total excursion) and the frequency increased until a peak acceleration of 8 g_n occurs (approximately 50 Hz).

A peak acceleration of 8 g_n is then maintained until the frequency is increased to 200 Hz.

For large batteries: from 7 Hz to a peak acceleration of 1 g_n is maintained until 18 Hz is reached. The amplitude is then maintained at 0.8 mm (1.6 mm total excursion) and the frequency increased until a peak acceleration of 2 g_n occurs (approximately 25 Hz). A peak acceleration of 2 g_n is then maintained until the frequency is increased to 200 Hz.

Cells and batteries meet this requirement if there is no leakage, no venting, no disassembly, no rupture and no fire during the test and after the test and if the open circuit voltage of each test cell or battery directly after testing in its third perpendicular mounting position is not less than 90% of its voltage immediately prior to this procedure. The requirement relating to voltage is not applicable to test cells and batteries at fully discharged states.

T.4 Shock

Test cells and batteries shall be secured to the testing machine by means of a rigid mount which will support all mounting surfaces of each test battery. Each cell or battery shall be subjected to a half-sine shock of peak acceleration of 150 g_n and pulse duration of 6 milliseconds. Each cell or battery shall be subjected to three shocks in the positive direction followed by three shocks in the negative direction of three mutually perpendicular mounting positions of the cell or battery for a total of 18 shocks.

However, large cells and large batteries shall be subjected to a half-sine shock of peak acceleration of 50 g_n and pulse duration of 11 milliseconds. Each cell or battery is subjected to three shocks in the positive direction followed by three shocks in the negative direction of each of three mutually perpendicular mounting positions of the cell for a total of 18 shocks.

本检测单位保证检测的客观公正性，并对委托单位的商业秘密履行保密义务；委托单位对样品的代表性和资料的真实性负责，本检测单位仅对样品负责，委托单位对于检测结果的使用、使用所产生的直接或间接损失及一切法律后果，本检测单位不承担任何经济和法律责任；本《检测报告》如无PONY专用章和批准人签字或被复制，则无效；任何对本《检测报告》未经授权的部分或全部转载、篡改、伪造或复制行为都是违法的，将被追究民事、行政甚至刑事责任。

防伪说明：(1)《检测报告》的报告编号是唯一的，即每一个报告编号仅对应唯一的《检测报告》；
(2)《检测报告》采用特制防伪纸张印制，纸张表面带有“PONY”防伪纹路，该防伪纹路不支持复印，即复制件不会带有“PONY”防伪纹路；
(3)《检测报告》采用的防伪纸张内部亦加带有高科技“PONY”防伪水印，只有在验钞机等紫外线照射下方可显出无色荧光防伪字样；
(4)《检测报告》所盖防伪骑缝章中的一部分加盖于本检测单位的留底报告上，《检测报告》与本检测单位留底报告的骑缝章应拼合完整无缺。

Pony Testing International Group

www.ponytest.com ☎Hotline 400-819-5688

Add: Yingzhi Building, No. 49-3, Suzhou Road, Haidian District, Beijing	Building 35, No. 680, Guiping Road, Xuhui District, Shanghai	Building 60 of Zhongxing Industry City, Chuangye Road, Nanshan District, Shenzhen	6th Floor, No. 190, Zhuzhou Road, Laoshan District, Qingdao
Tel: (010) 82618116	(021) 64851999	(0755) 26050909	(0532) 88706866
Fax: (010) 82619629	(021) 64856403	(0755) 26068336	(0532) 88706877
E-mail: pony@ponytest.com	cs@ponytest.com	sz@ponytest.com	qd@ponytest.com



Pony Testing International Group

Cells and batteries meet this requirement if there is no leakage, no venting, no disassembly, no rupture and no fire and if the open circuit voltage of each test cell or battery after testing is not less than 90% of its voltage immediately prior to this procedure. The requirement relating to voltage is not applicable to test cells and batteries at fully discharged states.

T.5 External short circuit

The cell or battery to be tested shall be temperature stabilized so that its external case temperature reaches 55 ± 2 °C and then the cell or battery shall be subjected to a short circuit condition with a total external resistance of less than 0.1 ohm at 55 ± 2 °C. This short circuit condition is continued for at least one hour after the cell or battery external case temperature has returned to 55 ± 2 °C.

Cells and batteries meet this requirement if their external temperature does not exceed 170 °C and there is no disassembly, no rupture and no fire during the test and within six hours after the test.

T.6 Impact / Crush

Impact (applicable to cylindrical cells greater than 20 mm in diameter)

The sample cell or component cell is to be placed on a flat smooth surface. A $15.8 \text{ mm} \pm 0.1 \text{ mm}$ diameter, at least 6 cm long, or the longest dimension of the cell, whichever is greater, Type 316 stainless steel bar is to be placed across the centre of the sample. A $9.1 \text{ kg} \pm 0.1 \text{ kg}$ mass is to be dropped from a height of 61 ± 2.5 cm at the intersection of the bar and sample in a controlled manner using a near frictionless, vertical sliding track or channel with minimal drag on the falling mass. The vertical track or channel used to guide the falling mass shall be oriented 90 degrees from the horizontal supporting surface.

The test sample is to be impacted with its longitudinal axis parallel to the flat surface and perpendicular to the longitudinal axis of the $15.8 \text{ mm} \pm 0.1 \text{ mm}$ diameter curved surface lying across the centre of the test sample. Each sample is to be subjected to only a single impact.

Crush (applicable to prismatic, pouch, coin/button cells and cylindrical cells not more than 20 mm in diameter)

A cell or component cell is to be crushed between two flat surfaces. The crushing is to be gradual with a speed of approximately 1.5 cm/s at the first point of contact. The crushing is to be continued until the first of the three options below is reached.

- (a) The applied force reaches $13 \text{ kN} \pm 0.78 \text{ kN}$;
- (b) The voltage of the cell drops by at least 100 mV; or
- (c) The cell is deformed by 50% or more of its original thickness.

Once the maximum pressure has been obtained, the voltage drops by 100 mV or more, or the cell is deformed by at least 50% of its original thickness, the pressure shall be released.

本检测单位保证检测的客观公正性，并对委托单位的商业秘密履行保密义务；委托单位对样品的代表性和资料的真实性负责，本检测单位仅对样品负责，委托单位对于检测结果的使用、使用所产生的直接或间接损失及一切法律后果，本检测单位不承担任何经济和法律责任；本《检测报告》如无PONY专用章和批准人签字或被复制，则无效；任何对本《检测报告》未经授权的部分或全部转载、篡改、伪造或复制行为都是违法的，将被追究民事、行政甚至刑事责任。

防伪说明：(1)《检测报告》的报告编号是唯一的，即每一个报告编号仅对应唯一的《检测报告》；
(2)《检测报告》采用特制防伪纸张印制，纸张表面带有“PONY”防伪纹路，该防伪纹路不支持复印，即复制件不会带有“PONY”防伪纹路；
(3)《检测报告》采用的防伪纸张内部亦加带有高科技“PONY”防伪水印，只有在验钞机等紫外线照射下方可显出无色荧光防伪字样；
(4)《检测报告》所盖防伪骑缝章中的一部分加盖于本检测单位的留底报告上，《检测报告》与本检测单位留底报告的骑缝章应拼合完整无缺。

Pony Testing International Group

www.ponytest.com ©Hotline 400-819-5688

Add: Yingzhi Building, No. 49-3, Suzhou Road, Haidian District, Beijing	Building 35, No. 680, Guiping Road, Xuhui District, Shanghai	Building 60 of Zhongxing Industry City, Chuangye Road, Nanshan District, Shenzhen	6th Floor, No. 190, Zhuzhou Road, Laoshan District, Qingdao
Tel: (010) 82618116	(021) 64851999	(0755) 26050909	(0532) 88706866
Fax: (010) 82619629	(021) 64856403	(0755) 26068336	(0532) 88706877
E-mail: pony@ponytest.com	esh@ponytest.com	sz@ponytest.com	qd@ponytest.com



Pony Testing International Group

A prismatic or pouch cell shall be crushed by applying the force to the widest side. A button/coin cell shall be crushed by applying the force on its flat surfaces. For cylindrical cells, the crush force shall be applied perpendicular to the longitudinal axis.

Each test cell or component cell is to be subjected to one crush only. The test sample shall be observed for a further 6 h. The test shall be conducted using test cells or component cells that have not previously been subjected to other tests.

Cells and component cells meet this requirement if their external temperature does not exceed 170 °C and there is no disassembly and no fire during the test and within six hours after this test.

T.7 Overcharge

The charge current shall be twice the manufacturer's recommended maximum continuous charge current. The minimum voltage of the test shall be as follows:

- (a) When the manufacturer's recommended charge voltage is not more than 18V, the minimum voltage of the test shall be the lesser of two times the maximum charge voltage of the battery or 22V.
- (b) When the manufacturer's recommended charge voltage is more than 18V, the minimum voltage of the test shall be 1.2 times the maximum charge voltage.

Tests are to be conducted at ambient temperature; the duration of the test shall be 24 hours.

Rechargeable batteries meet this requirement if there is no disassembly and no fire during the test and within seven days after the test.

T.8 Forced discharge

Each cell shall be forced discharged at ambient temperature by connecting it in series with a 12V D.C. power supply at an initial current equal to the maximum discharge current specified by the manufacturer.

The specified discharge current is to be obtained by connecting a resistive load of the appropriate size and rating in series with the test cell. Each cell shall be forced discharged for a time interval (in hours) equal to its rated capacity divided by the initial test current (in ampere).

Primary or rechargeable cells meet this requirement if there is no disassembly and no fire during the test and within seven days after the test.

本检测单位保证检测的客观公正性，并对委托单位的商业秘密履行保密义务；委托单位对样品的代表性和资料的真实性负责，本检测单位仅对样品负责，委托单位对于检测结果的使用、使用所产生的直接或间接损失及一切法律后果，本检测单位不承担任何经济和法律责任；本《检测报告》如无PONY专用章和批准人签字或被复制，则无效；任何对本《检测报告》未经授权的部分或全部转载、篡改、伪造或复制行为都是违法的，将被追究民事、行政甚至刑事责任。

防伪说明：(1)《检测报告》的报告编号是唯一的，即每一个报告编号仅对应唯一的《检测报告》；
 (2)《检测报告》采用特制防伪纸张印制，纸张表面带有“PONY”防伪纹路，该防伪纹路不支持复印，即复制件不会带有“PONY”防伪纹路；
 (3)《检测报告》采用的防伪纸张内部亦加带有高科技“PONY”防伪水印，只有在验钞机等紫外线照射下方可显出无色荧光防伪字样；
 (4)《检测报告》所盖防伪骑缝章中的一部分加盖于本检测单位的留底报告上，《检测报告》与本检测单位留底报告的骑缝章应拼合完整无缺。

Pony Testing International Group


www.ponytest.com ☎Hotline 400-819-5688

Add: Yingzhi Building, No.49-3, Suzhou Road, Haidian District, Beijing	Building 35, No.680, Guiping Road, Xuhui District, Shanghai	Building 606 of Zhongxing Industry City, Chuangye Road, Nanshan District, Shenzhen	6th Floor, No.190, Zhuzhou Road, Laoshan District, Qingdao
Tel: (010)82618116	(021)64851999	(0755)26050909	(0532)88706866
Fax: (010)82619629	(021)64856403	(0755)26068336	(0532)88706877
E-mail: pony@ponytest.com	cs@ponytest.com	sz@ponytest.com	qd@ponytest.com



Pony Testing International Group

VII、 TEST PROCEDURE

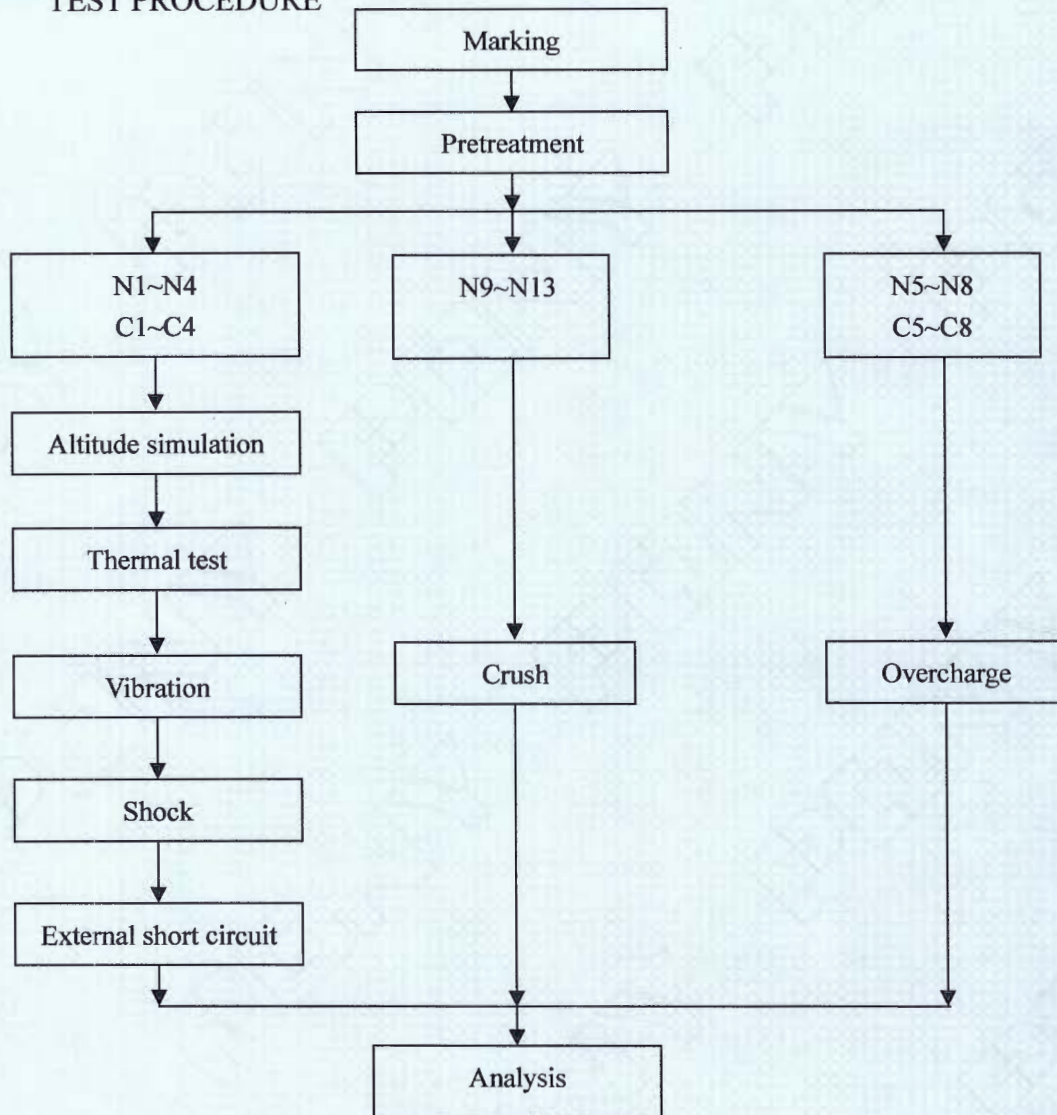

VIII、 MAIN TEST APPARATUS

SZSB-121 Rechargeable battery test system

SZSB-280 Vacuum chamber

SZSB-120 Temperature circulation chamber

SZSB-128 Vibration test instrument

SZSB-082 Shock test instrument

SZSB-281 Battery anti-explosion chamber

SZSB-077 DC regulated power supply

SZSB-198 Battery extrusion needling machine

SZSB-125 Electronic balance

SZSB-090 Digital multimeter

SZSB-185 Thermoelectric pair

本检测单位保证检测的客观公正性，并对委托单位的商业秘密履行保密义务；委托单位对样品的代表性和资料的真实性负责，本检测单位仅对样品负责，委托单位对于检测结果的使用、使用所产生的直接或间接损失及一切法律后果，本检测单位不承担任何经济和法律责任；本《检测报告》如无PONY专用章和批准人签字或被复制，则无效；任何对本《检测报告》未经授权的部分或全部转载、篡改、伪造或复制行为都是违法的，将被追究民事、行政甚至刑事责任。

防伪说明：(1)《检测报告》的报告编号是唯一的，即每一个报告编号仅对应唯一的《检测报告》；

(2)《检测报告》采用特制防伪纸张印制，纸张表面带有“PONY”防伪纹路，该防伪纹路不支持复印，即复制件不会带有“PONY”防伪纹路；

(3)《检测报告》采用的防伪纸张内部亦加带有高科技“PONY”防伪水印，只有在验钞机等紫外线照射下方可显出无色荧光防伪字样；

(4)《检测报告》所盖防伪骑缝章中的一部分加盖于本检测单位的留底报告上，《检测报告》与本检测单位留底报告的骑缝章应拼合完整无缺。

www.ponytest.com ©Hotline 400-819-5688

Add: YingzhiBuilding, No.49-3, Suzhou Road, Haidian District, Beijing

Tel: (010)82618116

Fax: (010)82619629

E-mail: pony@ponytest.com

Building 35, No.680, Guiping Road, Xuhui District, Shanghai

(021)64851999

(021)64856403

cs@ponytest.com

Building 60 of Zhongxing Industry City, Chuangye Road, Nanshan District, Shenzhen

(0755)26050909

(0755)26068336

sz@ponytest.com

6th Floor, No.190, Zhuzhou Road, Laoshan District, Qingdao

(0532)88706866

(0532)88706877

qd@ponytest.com



Pony Testing International Group

IX、 DATA

1. Altitude simulation

No.	Pre-test		After test		Mass loss (%)	Voltage loss (%)	Whether leakage, venting, disassembly, rupture, fire (Y/N)
	Mass (g)	Voltage (V)	Mass (g)	Voltage (V)			
N1	148.323	12.51	148.323	12.51	0.000	0.00	N
N2	149.084	12.51	149.084	12.51	0.000	0.00	N
N3	148.933	12.51	148.933	12.51	0.000	0.00	N
N4	148.849	12.51	148.849	12.51	0.000	0.00	N
C1	148.802	12.51	148.802	12.50	0.000	0.08	N
C2	148.928	12.51	148.927	12.51	0.001	0.00	N
C3	149.400	12.51	149.400	12.51	0.000	0.00	N
C4	149.109	12.51	149.109	12.51	0.000	0.00	N

2. Thermal test

No.	Pre-test		After test		Mass loss (%)	Voltage loss (%)	Whether leakage, venting, disassembly, rupture, fire (Y/N)
	Mass (g)	Voltage (V)	Mass (g)	Voltage (V)			
N1	148.323	12.51	148.282	12.35	0.028	1.28	N
N2	149.084	12.51	149.035	12.36	0.033	1.20	N
N3	148.933	12.51	148.894	12.36	0.026	1.20	N
N4	148.849	12.51	148.797	12.37	0.035	1.12	N
C1	148.802	12.50	148.764	12.36	0.026	1.12	N
C2	148.927	12.51	148.891	12.36	0.024	1.20	N
C3	149.400	12.51	149.358	12.36	0.028	1.20	N
C4	149.109	12.51	149.070	12.36	0.026	1.20	N

本检测单位保证检测的客观公正性，并对委托单位的商业秘密履行保密义务；委托单位对样品的代表性和资料的真实性负责，本检测单位仅对样品负责，委托单位对于检测结果的使用、使用所产生的直接或间接损失及一切法律后果，本检测单位不承担任何经济和法律后果；本《检测报告》如无PONY专用章和批准人签字或被复制，则无效；任何对本《检测报告》未经授权的部分或全部转载、篡改、伪造或复制行为都是违法的，将被追究民事、行政甚至刑事责任。

防伪说明：(1)《检测报告》的报告编号是唯一的，即每一个报告编号仅对应唯一的《检测报告》；
 (2)《检测报告》采用特制防伪纸张印制，纸张表面带有“PONY”防伪纹路，该防伪纹路不支持复印，即复制件不会带有“PONY”防伪纹路；
 (3)《检测报告》采用的防伪纸张内部亦加带有高科技“PONY”防伪水印，只有在验钞机等紫外线照射下方可显出无色荧光防伪字样；
 (4)《检测报告》所盖防伪骑缝章中的一部分加盖于本检测单位的留底报告上，《检测报告》与本检测单位留底报告的骑缝章应拼合完整无缺。

www.ponytest.com ☎Hotline 400-819-5688

Add: Yingzhi Building, No.49-3, Suzhou Road, Haidian District, Beijing
 Tel: (010)82618116
 Fax: (010)82619629
 E-mail: pony@ponytest.com

Building 35, No.680, Guiping Road, Xuhui District, Shanghai
 (021)64851999
 (021)64856403
 csh@ponytest.com

Building 607 Zhongxing Industry City, Chuangye Road, Nanshan District, Shenzhen
 (0755)26050909
 (0755)26068336
 sz@ponytest.com

6th Floor, No.190, Zhuzhou Road, Laoshan District, Qingdao
 (0532)88706866
 (0532)88706877
 qd@ponytest.com



Pony Testing International Group

3. Vibration

No.	Pre-test		After test		Mass loss (%)	Voltage loss (%)	Whether leakage, venting, disassembly, rupture, fire (Y/N)
	Mass (g)	Voltage (V)	Mass (g)	Voltage (V)			
N1	148.282	12.35	148.281	12.35	0.001	0.00	N
N2	149.035	12.36	149.035	12.36	0.000	0.00	N
N3	148.894	12.36	148.894	12.36	0.000	0.00	N
N4	148.797	12.37	148.796	12.36	0.001	0.08	N
C1	148.764	12.36	148.764	12.36	0.000	0.00	N
C2	148.891	12.36	148.890	12.36	0.001	0.00	N
C3	149.358	12.36	149.358	12.35	0.000	0.08	N
C4	149.070	12.36	149.070	12.36	0.000	0.00	N

4. Shock

No.	Pre-test		After test		Mass loss (%)	Voltage loss (%)	Whether leakage, venting, disassembly, rupture, fire (Y/N)
	Mass (g)	Voltage (V)	Mass (g)	Voltage (V)			
N1	148.281	12.35	148.281	12.35	0.000	0.00	N
N2	149.035	12.36	149.035	12.36	0.000	0.00	N
N3	148.894	12.36	148.893	12.35	0.001	0.08	N
N4	148.796	12.36	148.796	12.36	0.000	0.00	N
C1	148.764	12.36	148.764	12.36	0.000	0.00	N
C2	148.890	12.36	148.890	12.36	0.000	0.00	N
C3	149.358	12.35	149.358	12.35	0.000	0.00	N
C4	149.070	12.36	149.069	12.36	0.001	0.00	N

本检测单位保证检测的客观公正性，并对委托单位的商业秘密履行保密义务；委托单位对样品的代表性和资料的真实性负责，本检测单位仅对样品负责，委托单位对于检测结果的使用、使用所产生的直接或间接损失及一切法律后果，本检测单位不承担任何经济和法律后果；本《检测报告》如无PONY专用章和批准人签字或被复制，则无效；任何对本《检测报告》未经授权的部分或全部转载、篡改、伪造或复制行为都是违法的，将被追究民事、行政甚至刑事责任。

防伪说明：(1)《检测报告》的报告编号是唯一的，即每一个报告编号仅对应唯一的《检测报告》；
 (2)《检测报告》采用特制防伪纸张印制，纸张表面带有“PONY”防伪纹路，该防伪纹路不支持复印，即复制件不会带有“PONY”防伪纹路；
 (3)《检测报告》采用的防伪纸张内部亦加带有高科技“PONY”防伪水印，只有在验钞机等紫外线照射下方可见出无色荧光防伪字样；
 (4)《检测报告》所盖防伪骑缝章中的一部分加盖于本检测单位的留底报告上，《检测报告》与本检测单位留底报告的骑缝章应拼合完整无缺。

www.ponytest.com ☎Hotline 400-819-5688

Add: Yingzhi Building, No. 49-3, Suzhou Road, Haidian District, Beijing
 Building 35, No. 680, Guiping Road, Xuhui District, Shanghai
 Building 6 of Zhongxing Industry City, Chuangye Road, Nanshan District, Shenzhen
 6th Floor, No. 190, Zhuzhou Road, Laoshan District, Qingdao

Tel: (010)82618116

(021)64851999

(0755)26050909

(0532)88706866

Fax: (010)82619629

(021)64856403

(0755)26068336

(0532)88706877

E-mail: pony@ponytest.com

cs@ponytest.com

sz@ponytest.com

qd@ponytest.com

Pony Testing International Group



Pony Testing International Group

5. External short circuit

No.	Peak temperature (°C)	Whether disassembly, rupture, fire (Y/N)
N1	55	N
N2	56	N
N3	58	N
N4	55	N
C1	57	N
C2	55	N
C3	56	N
C4	55	N

6. Crush

No.	Peak temperature (°C)	Whether disassembly, fire (Y/N)
N9	31	N
N10	29	N
N11	33	N
N12	35	N
N13	38	N

7. Overcharge

No.	Whether disassembly, fire (Y/N)
N5	N
N6	N
N7	N
N8	N
C5	N
C6	N
C7	N
C8	N

8. Forced discharge

N/A (Not applicable)

本检测单位保证检测的客观公正性，并对委托单位的商业秘密履行保密义务；委托单位对样品的代表性和资料的真实性负责，本检测单位仅对样品负责，委托单位对于检测结果的使用、使用所产生的直接或间接损失及一切法律后果，本检测单位不承担任何经济和法律责任；本《检测报告》如无PONY专用章和批准人签字或被复制，则无效；任何对本《检测报告》未经授权的部分或全部转载、篡改、伪造或复制行为都是违法的，将被追究民事、行政甚至刑事责任。

防伪说明：(1)《检测报告》的报告编号是唯一的，即每一个报告编号仅对应唯一的《检测报告》；
 (2)《检测报告》采用特制防伪纸张印制，纸张表面带有“PONY”防伪纹路，该防伪纹路不支持复印，即复制件不会带有“PONY”防伪纹路；
 (3)《检测报告》采用的防伪纸张内部亦加带有高科技“PONY”防伪水印，只有在验钞机等紫外线照射下方可见出无色荧光防伪字样；
 (4)《检测报告》所盖防伪骑缝章中的一部分加盖于本检测单位的留底报告上，《检测报告》与本检测单位留底报告的骑缝章应拼合完整无缺。

www.ponytest.com ☎Hotline 400-819-5688

Add: Yingzhi Building, No.49-3, Suzhou Road, Haidian District, Beijing	Building 35, No.680, Guiping Road, Xuhui District, Shanghai	Building 60 of Zhongxing Industry City, Chuangye Road, Nanshan District, Shenzhen	6th Floor, No.190, Zhuzhou Road, Laoshan District, Qingdao
Tel: (010)82618116	(021)64851999	(0755)26050909	(0532)88706866
Fax: (010)82619629	(021)64856403	(0755)26068336	(0532)88706877
E-mail: pony@ponytest.com	cs@ponytest.com	sz@ponytest.com	qd@ponytest.com